
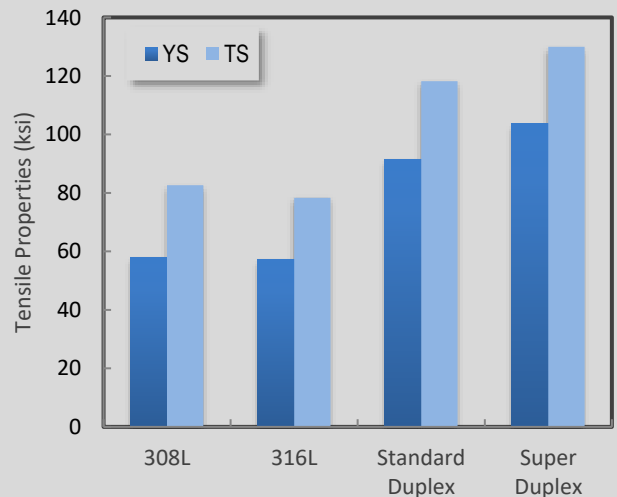


PREMIARC® DW-329AP [AWS A5.22 E2209T1-1/4]
PREMIARC® DW-2209 [AWS A5.22 E2209T1-1/4]
PREMIARC® DW-2594 [AWS A5.22 E2594T1-1/4]

Features and typical fields of application

- Standard and super duplex stainless steel flux cored wires with high tensile strength and corrosion resistance compared to 308L/316L type austenitic stainless steel for petrochemical industry, chemical tanker or desalination process equipment as typical application.
- All positional welding with either 75%Ar-25%CO₂ gas or 100%CO₂
- Flat bead profile with easy mig-gun operation in the flat and horizontal positions as well as out of position contribute to productivity.


DW-329AP: **Standard duplex** 22Cr-9Ni-0.1N /S31803, S32205 etc. **with excellent weldability in 3G**
DW-2209: **Standard duplex** 22Cr-9Ni-0.1N /S31803, S32205 etc. **with toughness down to -40°F**
DW-2594: **Super duplex** 25Cr-9Ni-4Mo-0.2N/ S32750, S32760 etc.

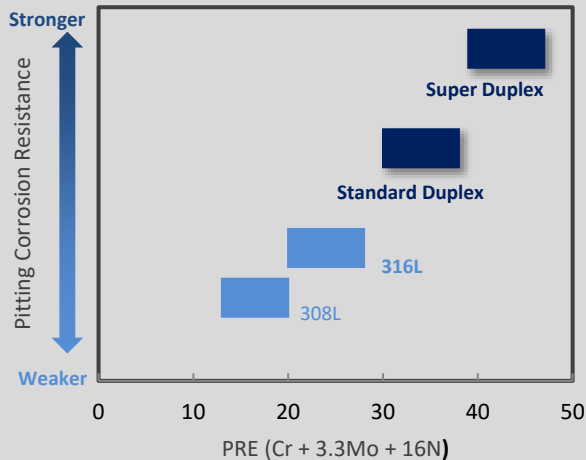

Typical chemical composition of metal test per AWS A5.22

	Shielding Gas	C	Si	Mn	Ni	Cr	Mo	N	PREN *	FNW **
DW-329AP	75%Ar-25%CO ₂	0.02	0.7	0.7	9.4	23.3	3.4	0.14	37	49
DW-2209		0.03	0.5	0.7	9.4	23.0	3.3	0.14	36	43
DW-2594		0.03	0.5	1.2	9.5	25.5	3.8	0.22	42	52

*: Pitting Resistance Equivalent Number = Cr+3.3(Mo+0.5W)+16N % **: Ferrite Number by WRC Diagram (1992)

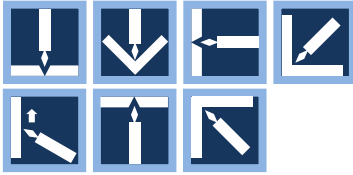

PREMIARC™ DW-329AP [AWS A5.22 E2209T1-1/4]
PREMIARC™ DW-2209 [AWS A5.22 E2209T1-1/4]
PREMIARC™ DW-2594 [AWS A5.22 E2594T1-1/4]

Typical mechanical property of weld metal per AWS

	Shielding Gas	0.2% PS (ksi)	TS (ksi)	EI (%)	CVN (ft-lbs)	
					-40°F	32°F
DW-329AP	75%Ar-25%CO ₂	90	121	28	-	38
DW-2209		91	118	28	44	54
DW-2594		104	130	28	28	41

Approval

LR, CWB (DW-329AP, DW-2209, DW-2594)
 ABS, DNV-GL (DW-329AP, DW-2594)

Recommended welding conditions and deposition rate

Wire Dia.	Wire Feed Speed (in/min)	Welding Current (A)	Arc Voltage (V)	Deposition Rate (lbs/hr)	Wire Stick-Out	Shielding Gas Flow Rate (CFH)
0.045"	210	130	24-26	5.0	5/8-3/4"	40-50
	275	155	25-27	6.0		
	330	175	26-28	6.8		
	380	190	27-29	8.0		
	440	210	28-30	9.5		
	540	230	28-31	10.6		
	610	250	30-33	12.0		

Table shown are approximate values that will vary depending on welding conditions (WESO, Cable length etc.).
 Arc voltage shown are for straight CO₂ shielding gas. For 75%Ar-25%CO₂ use two volts less than shown.

Available Products

Wire Dia.	0.045"	Package	28 lbs spool
-----------	--------	---------	--------------

DISCLAIMER

- Information in this material, such as chemical compositions and mechanical properties, is typical or an example for explaining the features and performances of our products, and it does not mean guarantee unless otherwise it is specified.
- Information contained herein is subject to change without notice. Please kindly contact Kobelco for latest information.



WARNING: This product can expose you to chemicals including Nickel and Titanium Dioxide, which are known to the State of California to cause cancer, and Chromium, which is known to the State of California to cause cancer and birth defects or other reproductive harm. For more information go to www.P65Warnings.ca.gov.

KOBELCO WELDING OF AMERICA INC.



4755 Alpine Drive, Suite 250, Stafford, Texas 77477
 TEL: 281-240-5600 FAX: 281-240-5625
<http://www.kobelcowelding.com>